

The Effect of Chlorhexidine Application on the Microtensile Bond Strength and Durability of a Total-Etch Adhesive

Hila Hajizadeh, Maryam Bojarpour¹, Alireza Borouzinia², Fatemeh Namdar³

Department of Restorative and Cosmetic Dentistry, School of Dentistry, Mashhad University of Medical Sciences, Mashhad, ¹Department of Periodontics, School of Dentistry, Bojnord University of Medical Sciences, Bojnord, ²Dental Research Center, Mashhad University of Medical Sciences, ³Dental Materials Research Center, Mashhad University of Medical Sciences, Mashhad, Iran

Abstract

Aim: The aim of this study was to evaluate the effect of chlorhexidine (CHX) on resin–dentin microtensile bond strength (μ TBS) after 6-month aging and to compare with sodium hypochlorite. **Materials and Methods:** A total of 40 extracted human third molar teeth were mounted in the acrylic resin. Flat occlusal surfaces of dentin were exposed, and after acid etching, the samples were divided randomly into four groups as follows: (a) Control group: Single Bond adhesive resin was applied. (b) The dentin surfaces were exposed to 2% CHX, and then, Single Bond was applied. (c) Dentin surfaces were treated by 5.25% sodium hypochlorite; after rinsing and drying, Single Bond was applied. (d) At first, 5.25% sodium hypochlorite was applied for 30 s, and then, 2% CHX and Single Bond adhesive were applied. Finally, Filtek P60 composite was bonded on the dentin surface. The samples of each group were divided into two subgroups of 24 h and 6 months. μ TBS tests were performed using universal testing machine. Afterward, modes of failures were investigated. The statistical analyses were carried out using ANOVA, *t*-test, and Dunnett's test. **Results:** The mean of μ TBS for the 24-h and 6-month groups was 15.19 and 10.99 MPa, respectively. Bond strength of all groups except Group D decreased after 6 months, and this bond strength reduction in Group C was more than other groups. Most failure modes were in adhesive type. **Conclusions:** The use of CHX did not have better preservation of μ TBS when compared to control group. Use of hypochlorite is not recommended.

Keywords: Chlorhexidine, matrix metalloproteinase, microtensile bond strength, sodium hypochlorite

INTRODUCTION

Despite technical and chemical improvements in dental materials, microleakage is yet a problem that influences resin–dentin interfaces. Microleakage is mostly attributed to polymerization shrinkage, which causes postoperative sensitivity, secondary caries, and pulpal injuries.^[1]

The destruction of the hybrid layer at the resin–dentin interface could compromise the entire restoration, thereby lead to restoration failure. Hybrid layer degradation could occur for various reasons, including water absorption and hydrolysis, fatigue forces, thermal expansion, and matrix metalloproteinase enzymes (MMPs). MMPs-2, 8, and 9 are known as active proteases in the oral cavity that can degrade collagen fibers in the hybrid layer.^[2] These enzymes are present in the dentin and are secreted by odontoblasts in the form of a proenzyme, which is an inactive form of the enzyme and requires extracellular activation. Acid etching

and self-etching adhesive systems activate these enzymes.^[3] In addition, the presence of acidic environments or a temperature increase activates dentin MMPs.^[4] There are some inhibitory factors which prevent the activity of MMPs; for instance, chlorhexidine (CHX) digluconate has been known to be an inhibitor of MMPs-2, 8, and 9.^[5]

In addition, problems associated with microleakage could be exacerbated by the microbial contamination of the cavity. This would be due to the incomplete caries removal

Address for correspondence: Dr. Fatemeh Namdar,
Dental Materials Research Center, Mashhad University of Medical Sciences,
Mashhad, Iran.
E-mail: f.namdar90@gmail.com

This is an open access journal, and articles are distributed under the terms of the Creative Commons Attribution-NonCommercial-ShareAlike 4.0 License, which allows others to remix, tweak, and build upon the work non-commercially, as long as appropriate credit is given and the new creations are licensed under the identical terms.

For reprints contact: reprints@medknow.com

How to cite this article: Hajizadeh H, Bojarpour M, Borouzinia A, Namdar F. The effect of chlorhexidine application on the microtensile bond strength and durability of a total-etch adhesive. *Eur J Gen Dent* 2020;9:17-22.

Received: 06th April, 2019 **Revision:** 23rd June, 2019

Accepted: 07th October, 2019 **Publication:** 02nd January, 2020

Access this article online

Quick Response Code:



Website:
www.ejgd.org

DOI:
10.4103/ejgd.ejgd_50_19

and the presence of bacteria in the cavity. These bacteria grow, and their toxins penetrate into the pulp and cause irritation and inflammation even with the perfect seal of the cavity.^[6] One way of eliminating or reducing bacteria from the cavity is the use of antiseptic solutions. Some studies have suggested the use of antibacterial agents such as CHX after cavity preparation and before restoration.^[6,7] CHX is a broad-spectrum antimicrobial agent with cationic properties, and its antibacterial performance is comparable to that of sodium hypochlorite.^[8] The minimum concentration of CHX inhibiting the function of MMP-9 is 0.002%. However, the function of the more sensitive MMP-2 enzyme is inhibited at a concentration of 0.0001% CHX. MMP-8 is also inhibited at a concentration of 0.02% CHX.^[5]

The application of cavity disinfectants with adhesive resins could change the ability of adhesives to seal the dentin. In addition, cavity disinfectants could exert a negative effect on the bond strength of restorative materials to dentin structures.^[9] Some studies have examined the effects of cavity disinfectants on the bond strength of resin composites to the dentin and reported varying amounts of bond strength, depending on the active components in these materials and the types of adhesive systems.^[1,8] Inconsistencies in findings could be attributed to the limitations of bond strength tests. If cavity disinfectants interfere with the wettability of hydrophilic resins, the use of these materials could be problematic. In addition, it has been shown that cavity disinfectants, acting as a wetting agent before the use of adhesives, could improve adhesion to dentin and enamel.^[10]

Given the desired properties of CHX in inhibiting MMPs enzymes, this study was done aimed at evaluating the effects of protease inhibition by CHX on the resin–dentin microtensile bond strength (μ TBS) after 6 months of aging and comparing it with sodium hypochlorite. Our null hypothesis was that protease inhibition by CHX would not affect the μ TBS after aging.

MATERIALS AND METHODS

In this study, 40 extracted caries-free human third molar teeth were used. Written informed consent was obtained from all patients. After calculus and debris removal, the teeth were stored in the thymol solution at 4°C and used within 2 months of extraction. After mounting the teeth in the acrylic resin, each sample was cut using a low-speed diamond saw (IsoMet 4000, Buehler, USA). The sections were in such a way that occlusal enamel surfaces were removed, and dentin surfaces were remained 1 mm more inside than dentin–enamel junction, perpendicular to the longitudinal axis of the tooth. Next, the sample surfaces were polished by silicon carbide 400, 600, 800, and 1000 grits. Dentin surfaces were etched by 35% phosphoric acid (3M ESPE/Scotchbond™ Etchant, Dental Products, St. Paul, USA) for 15 s, after rinsing for 10 s; they were then dried with gentle air spray (before the complete drying of the dentin surfaces). Afterward, the samples were divided randomly into four groups of ten as follows:

- a. Control group: Adper Single Bond adhesive resin (3M ESPE, Adhesive, St. Paul, USA) was applied to the dentin surface, according to the manufacturer's instructions
- b. The dentin surfaces were exposed to 2% CHX (Consepsis, Ultradent, USA). Next, they were dried slightly with cotton, and the Adper Single Bond adhesive resin was applied
- c. For 30 s, 5.25% sodium hypochlorite was applied to the dentin surfaces. Afterward, the Single Bond adhesive resin was applied after rinsing and drying with cotton
- d. At first, 5.25% sodium hypochlorite was applied to the dentin surface for 30 s; it was then rinsed and rehydrated by 2% CHX for 30 s. In the end, the Single Bond adhesive resin was applied.

In all groups, after removing the adhesive excess and solvent vapors, the adhesive was cured by a light cure device (Bluephase, Ivoclar Vivadent, Austria) for 20 s, using a soft start pattern. The teeth were surrounded by toffel myer transparent matrix strips, and then, two layers of the composite resin Filtek P60 (3M ESPE, Dental Products, ST. Paul, USA) with a 3-mm height were placed on them; next, each layer was cured for 40 s, according to the manufacturer's instructions.

Each group was divided randomly into two subgroups as follows:

- Group A in which the μ -TBS test was performed 24 h after the preparation
- The samples in Group B were stored for 6 months at 100% humidity and 37°C, and then, the μ -TBS test was performed.

After a 24-h storage period in distilled water, the specimens of Group A were subjected to the μ TBS test, while Group B specimens were kept in distilled water for 6 months before doing the μ TBS test. Next, cutoffs with a thickness of 1 mm were produced using a low-speed diamond saw. All sections were evaluated by a stereomicroscope, and samples containing bubbles or enamel remnants in the composite–dentin interface were removed. Perfect sections were mounted and cut again to provide beams with the dimensions of $1 \times 1 \text{ mm}^2$ and 10 mm long. On average, 3–5 beams were obtained from each tooth. As five teeth were used in each group, 15–25 beams were evaluated in each experimental group. After examination by a stereomicroscope and the selection of healthy beams, the samples were assembled carefully using the mitreapel adhesive on a pair of resin plexiglasses to test the μ TBS. The μ TBS test was performed by the universal testing machine of STM device (STM 20, Santem) at a speed of 0.5 mm/min. The μ TBS was calculated by dividing the debonding force by the composite–dentin beam's cross-sectional area in MPa units. After the test, failure modes were investigated by a stereomicroscope with the magnification of $\times 40$, with failure modes classified as adhesive, cohesive, and mixed. The statistical analysis was performed by ANOVA, *t*-test, and Dunnett's test at the significant level of $\alpha = 0.05$.

RESULTS

The Kolmogorov–Smirnov test showed the normal distribution of the data. In a 24-h testing period, the highest and lowest μ TBS were related to the control Group (A) and the sodium hypochlorite + CHX (D) group, respectively. In addition, in the 6-month testing period, Group A and chad showed the highest and lowest μ TBS, respectively [Figure 1 and Table 1].

Pretreatment by sodium hypochlorite + CHX (Group D) resulted in a significantly lower bond strength in a 24-h testing period. The 6-month aging period resulted in the significant μ TBS reduction of Group C. There was no significant difference between the 24-h and 6-month tested groups in failure modes, yet most of the failures were adhesives [Table 2].

DISCUSSION

Sodium hypochlorite is a proteolytic agent that eliminates organic compounds effectively and is used routinely for collagen fibers removal.^[11] The remnants of sodium hypochlorite and its byproduct (oxygen) affect the adhesive polymerization process negatively and reduce the bond strength. This effect is maximized when sodium hypochlorite is added to the composition of total etch systems.^[12] According to the results of this study, it seems that sodium hypochlorite cannot maintain

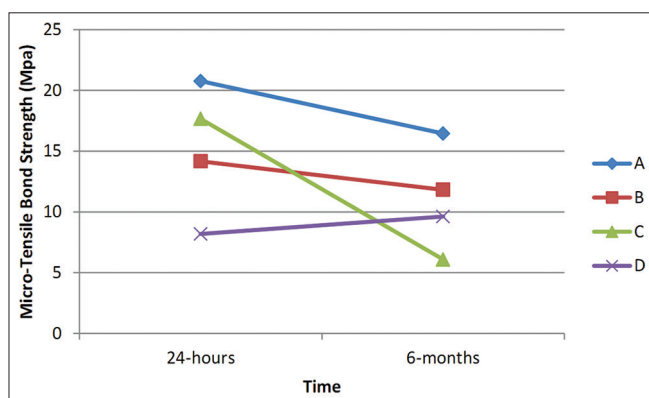


Figure 1: Comparing the microtensile bond strengths between groups at 24-h and 6-months testing periods (A: control group, B: 2% chlorhexidine, C: 5.25% sodium hypochlorite, and D: 2% chlorhexidine + sodium hypochlorite)

Table 1: The microtensile bond strengths (mean ± standard deviation) at 24-h and 6-month testing period

Time	Groups	Mean ± SD
24 h	A: Control group	20.76±6.5
	B: 2% CHX	14.17±3.65
	C: Sodium hypochlorite	17.66±5.08
	D: 2% CHX + sodium hypochlorite	8.19±1.3
6 months	A: Control group	16.45±6.74
	B: 2% CHX	11.82±4.01
	C: Sodium hypochlorite	6.08±2.71
	D: 2% CHX + sodium hypochlorite	9.62±3.11

CHX – Chlorhexidine, SD – Standard deviation

bond durability as expected. Since comparisons between the 24-h and 6-month tested groups showed a significant reduction in the μ TBS, the use of sodium hypochlorite is not recommended. Past research shows that this type of interference is attributed to the oxidizing effect of sodium hypochlorite and its remnants on resin polymerization.^[13] The use of sodium ascorbate on dentin surfaces has been recommended for neutralizing sodium hypochlorite. Sodium ascorbate is a reducing agent that reacts with the byproducts of sodium hypochlorite and removes them, with the end products of which being oxalic acid and L-threonic acid that are both water soluble. As a result, sodium ascorbate converts the oxidized dentin into a reduced substrate, facilitates complete resin polymerization, and increases the adhesive bond strength.^[14]

Another way of maintaining the bond strength is to use MMP inhibitors such as CHX. In this study, the μ TBS of the CHX group had no significant difference with that of the control group at 24-h and 6-month intervals. CHX digluconate is a bis-cationic biguanide compound with antimicrobial effects on *Enterococcus faecalis*, which is recommended as a broad-spectrum disinfectant for the disinfection of dentin surfaces.^[15]

The CHX release pattern is slow and continuous over a long period of time. Singh *et al.* reported that the release of CHX from the orthodontic composite resin was continuous in 60 days.^[16] Grazielle Magro *et al.* showed that various formulations of 2% CHX (solution, gel, CHX-Plus, Consepsis) produced more debris and smear layers than 17% ethylenediaminetetraacetic acid and 2.5% sodium hypochlorite. However, none of these formulations and depositions interfered with the push-out bond strength of sealers to the dentin.^[17] In addition, CHX is an aqueous solution, and its inhibitory effect on MMPs (especially MMP 2, 8, and 9) and cysteine cathepsins lead to a significant reduction in oral microorganisms, such as streptococcus mutants in oral cavities. As a result, the past research proves the stability of the resin–dentin bond for a long time.^[5]

In addition, CHX has other effects on the dentin structure. It has two strong and positive ionic charges that bond to the negative charges of phosphate groups in the mineralized dentin crystallites or carboxylate groups in the collagenous matrix; furthermore, CHX improves the bond strength by increasing the free energy of enamel and dentin surfaces. Using the inhibitory effects of MMPs, CHX causes the long-term durability of the hybrid layer and the bond strength in mineralized and demineralized dentin substrates.^[18]

CHX molecules tend to get trapped under resin adhesives within the collagenous interfibrillar spaces and preserve their connection to collagenous fibrils after adhesive/primer application. In addition, the collagen fibrils treated with CHX are surrounded by adhesive monomers and can preserve CHX at the interface, with a long-term inhibitory function.^[18,19]

In fact, the 2% CHX solution is composed of 2% gluconate and 98% water, which can wet the surface fully after application. Hence, the remaining humidity may decrease the functional

Table 2: Distribution of failure modes (in percentage) between groups at 24-h and 6-month testing period

Time × failure mode cross tabulation				
Group	Failure mode			Total
	Adhesive	Cohesive	Mixed	
A				
Time				
24 h				
Count	7	2	2	11
Percentage within time	63.6	18.2	18.2	100.0
6 months				
Count	8	2	1	11
Percentage within time	72.7	18.2	9.1	100.0
Total				
Count	15	4	3	22
Percentage within time	68.2	18.2	13.6	100.0
B				
Time				
24 h				
Count	8	1	2	11
Percentage within time	72.7	9.1	18.2	100.0
6 months				
Count	9	1	1	11
Percentage within time	81.8	9.1	9.1	100.0
Total				
Count	17	2	3	22
Percentage within time	77.3	9.1	13.6	100.0
C				
Time				
24 h				
Count	10		1	11
Percentage within time	90.9		9.1	100.0
6 months				
Count	10		1	11
Percentage within time	90.9		9.1	100.0
Total				
Count	20		2	22
Percentage within time	90.9		9.1	100.0
D				
Time				
24 h				
Count	10		1	11
Percentage within time	90.9		9.1	100.0
6 months				
Count	10		1	11
Percentage within time	90.9		9.1	100.0
Total				
Count	20		2	22
Percentage within time	90.9		9.1	100.0

A: Control group, B: 2% CHX, C: Sodium hypochlorite, D: 2% CHX + sodium hypochlorite. CHX – Chlorhexidine

properties of the monomers.^[20] If water is used, water hydrogen will bond to collagen fibrils instead of CHX, thereby decreasing the bond strength.^[18] Therefore, in the current study, dentin surfaces were not rinsed but were just dried using mild air spraying.

Since the used CHX solution was not rinsed, and only its remnants were removed using mild air spray, there are concerns about interactions with adhesive systems. It seems that incorporating CHX into the adhesives would necessitate adding water to the formula and compromising the adhesives' effectiveness.^[21] Nevertheless, different studies show that the use of CHX does not improve the bond strength and physical properties.^[22,23]

Another study demonstrated that although CHX treatment interfered with the immediate bond strength (due to chemical interactions among CHX, phosphate, and deposition formation), the bond strength obtained after a 6-month period of cycling loading was stable due to the long-term integrity of the hybrid layer and the MMPs inhibitory effect of CHX. CHX could inhibit the degradation of the exposed collagen, thereby improving the longevity of the bond strength.^[24,25] Loguercio *et al.* reported that stable bond strengths were maintained for 6 months after CHX treatment, regardless of the CHX application time and concentration.^[26] Another study showed that even at the low concentrations of CHX and within a short time of application, CHX affected hybrid layer degradation, thereby influencing the *in vitro* bond strength positively over time.^[27] In addition, Leitune *et al.* showed that CHX application was not effective in improving the bond strength of fiber posts cemented to the radicular dentin after 6 months.^[22]

It has been demonstrated that CHX incorporation into the acidic conditioner can be useful in enhancing the long-term stability of collagenous fibrils in the hybrid layer against host-derived MMPs, with no need for additional steps in the bonding process.^[28] When CHX was incorporated into the primer of the self-etch adhesive, CHX could preserve the dentin bond strength as long as the CHX concentration in the primer was over or equal to 0.1%.^[29] In a study, Pomacóndor-Hernández *et al.* concluded that 2% CHX incorporation as a component of Adper Scotchbond SE did not influence the immediate bond strength, neither was any reduction observed in the bond strength within 3–6 months from water storage.^[30]

A reason for the discrepancies between the results of different studies is that the behavior of MMPs enzymes may be different in *in vitro* and *in vivo* conditions; in addition, time plays a major role in this process. In the present study, the samples were stored for 6 months at 100% humidity and 37°C, and then, μ -TBS tests were performed. The highest μ TBS were related to the control Group (A) in the 24-h and 6-month testing periods. The finding based on which the application of CHX + sodium hypochlorite (Group D) showed a higher μ TBS after a 6-month storage period was unexpected compared to the 24-h period, yet the difference was statistically insignificant. The difference could have been due to the bias in testing or differences in dentin substrates. For more precise evaluations, it is recommended that the sample size be increased. It is worth noting that the μ TBS test is very sensitive, and gaining precise results is affected by external factors.

In the current study, the prevalence of adhesive failure was more than other failures at the composite–dentin interface.

However, Nour El-din *et al.* and Gurgan *et al.* reported that there was no correlation between the failure mode and the bond strength value.^[31,32]

Since water absorption plays an important role in the bond degradation of resin–dentin in the *in vivo* environment during the relevant time, aqueous environments are used in the studies as a reliable medium to simulate oral cavity conditions.^[33] In contrast, Kitasako *et al.* and Shafiei and Memarpour reported that to prevent microorganism growth, the water storage of specimens had to be changed on a daily basis during the study; however, this daily change might damage the resin–dentin interface and decrease the bond strength.^[34,35] Therefore, in the current study, the water storage medium was changed on a weekly basis.

The 6-month aging resulted in a reduction in the μ TBS of all specimens, except for Group D (CHX + sodium hypochlorite). The bond strength reduction in Group C (sodium hypochlorite) was significant and more than in other groups. The 6-month water storage resulted in the least reduction in the bond strength in Group B (CHX) among other groups. Regardless of the reasons that made the CHX group obtain more stable bond strength over the 6-month period, it could be considered a good option for dentists to disinfect cavity preparations. This *in vitro* investigation was conducted under static conditions on flat dentin surfaces. Various factors, such as thermal, mechanical, and chemical factors, as well as fatigue stresses affect the bond strength. These are the limitations of the present study. Further *in vitro* researches are needed to evaluate the MMP inhibitory effect of CHX on prevention of collagen degradation and improve the bond strength longevity.

CONCLUSIONS

- The highest bond strength was related to the control group
- The use of CHX did not have better preservation of bond strength when compared to the control group
- Bond strength of all groups except Group D (CHX + sodium hypochlorite) decreased after 6 months, and this bond strength reduction in Group C was more than other groups
- The 6-month water storage period resulted in the least bond strength reduction in Group B (CHX) when compared to other groups.

Acknowledgment

This research was based on a research project No. 920026 and supported by a grant from the Dental research center, Mashhad University of Medical Sciences, Mashhad, Iran.

Financial support and sponsorship

This study was financially supported by the Dental Research Center, Mashhad University of Medical Sciences, Mashhad, Iran.

Conflicts of interest

There are no conflicts of interest.

REFERENCES

1. de Castro FL, de Andrade MF, Duarte Júnior SL, Vaz LG, Ahid FJ. Effect of 2% chlorhexidine on microtensile bond strength of composite to dentin. *J Adhes Dent* 2003;5:129-38.
2. Pashley DH, Tay FR, Imazato S. How to increase the durability of resin-dentin bonds. *Compend Contin Educ Dent* 2011;32:60-4, 66.
3. Nagase H, Visse R, Murphy G. Structure and function of matrix metalloproteinases and TIMPs. *Cardiovasc Res* 2006;69:562-73.
4. Pashley DH, Tay FR, Yiu C, Hashimoto M, Breschi L, Carvalho RM, *et al.* Collagen degradation by host-derived enzymes during aging. *J Dent Res* 2004;83:216-21.
5. Gendron R, Grenier D, Sorsa T, Mayrand D. Inhibition of the activities of matrix metalloproteinases 2, 8, and 9 by chlorhexidine. *Clin Diagn Lab Immunol* 1999;6:437-9.
6. Brännström M. The cause of postrestorative sensitivity and its prevention. *J Endod* 1986;12:475-81.
7. Gultz J, Do L, Boylan R, Kaim J, Scherer W. Antimicrobial activity of cavity disinfectants. *Gen Dent* 1999;47:187-90.
8. Zhang SC, Kern M. The role of host-derived dentinal matrix metalloproteinases in reducing dentin bonding of resin adhesives. *Int J Oral Sci* 2009;1:163-76.
9. Tulunoglu O, Ayhan H, Olmez A, Bodur H. The effect of cavity disinfectants on microleakage in dentin bonding systems. *J Clin Pediatr Dent* 1998;22:299-305.
10. Al Qahtani MQ, Platt JA, Moore BK, Cochran MA. The effect on shear bond strength of rewetting dry dentin with two desensitizers. *Oper Dent* 2003;28:287-96.
11. Frankenberger R, Krämer N, Oberschachtsiek H, Petschelt A. Dentin bond strength and marginal adaption after NaOCl pre-treatment. *Oper Dent* 2000;25:40-5.
12. Vongphan N, Senawongse P, Somsiri W, Harnirattisai C. Effects of sodium ascorbate on microtensile bond strength of total-etching adhesive system to NaOCl treated dentine. *J Dent* 2005;33:689-95.
13. Yiu CK, Garcia-Godoy F, Tay FR, Pashley DH, Imazato S, King NM, *et al.* A nanoleakage perspective on bonding to oxidized dentin. *J Dent Res* 2002;81:628-32.
14. Nagpal R, Tewari S, Gupta R. Effect of various surface treatments on the microleakage and ultrastructure of resin-tooth interface. *Oper Dent* 2007;32:16-23.
15. Oliveira DP, Barbizam JV, Trope M, Teixeira FB. *In vitro* antibacterial efficacy of endodontic irrigants against *Enterococcus faecalis*. *Oral Surg Oral Med Oral Pathol Oral Radiol Endod* 2007;103:702-6.
16. Singh C, Dua V, Vyas M, Verma S. Evaluation of the antimicrobial and physical properties of an orthodontic photo-activated adhesive modified with an antiplaque agent: An *in vitro* study. *Indian J Dent Res* 2013;24:694-700.
17. Grazielle Magro M, Kuga MC, Regina Victorino K, Vázquez-García FA, Aranda-García AJ, Faria-Junior NB, *et al.* Evaluation of the interaction between sodium hypochlorite and several formulations containing chlorhexidine and its effect on the radicular dentin – SEM and push-out bond strength analysis. *Microsc Res Tech* 2014;77:17-22.
18. Kim J, Uchiyama T, Carrilho M, Agee KA, Mazzoni A, Breschi L, *et al.* Chlorhexidine binding to mineralized versus demineralized dentin powder. *Dent Mater* 2010;26:771-8.
19. Hebling J, Pashley DH, Tjäderhane L, Tay FR. Chlorhexidine arrests subclinical degradation of dentin hybrid layers *in vivo*. *J Dent Res* 2005;84:741-6.
20. Hiraishi N, Yiu CK, King NM, Tay FR. Effect of 2% chlorhexidine on dentin microtensile bond strengths and nanoleakage of luting cements. *J Dent* 2009;37:440-8.
21. Al-Musallam TA, Evans CA, Drummond JL, Matasa C, Wu CD. Antimicrobial properties of an orthodontic adhesive combined with cetylpyridinium chloride. *Am J Orthod Dentofacial Orthop* 2006;129:245-51.
22. Leitune VC, Collares FM, Werner Samuel SM. Influence of chlorhexidine application at longitudinal push-out bond strength of fiber posts. *Oral Surg Oral Med Oral Pathol Oral Radiol Endod* 2010;110:e77-81.
23. De Munck J, Mine A, Van den Steen PE, Van Landuyt KL, Poitevin A, Opendakker G, *et al.* Enzymatic degradation of adhesive-dentin

- interfaces produced by mild self-etch adhesives. *Eur J Oral Sci* 2010;118:494-501.
24. Cecchin D, de Almeida JF, Gomes BP, Zaia AA, Ferraz CC. Influence of chlorhexidine and ethanol on the bond strength and durability of the adhesion of the fiber posts to root dentin using a total etching adhesive system. *J Endod* 2011;37:1310-5.
 25. Breschi L, Cammelli F, Visintini E, Mazzoni A, Vita F, Carrilho M, *et al.* Influence of chlorhexidine concentration on the durability of etch-and-rinse dentin bonds: A 12-month *in vitro* study. *J Adhes Dent* 2009;11:191-8.
 26. Loguercio AD, Stanislawczuk R, Polli LG, Costa JA, Michel MD, Reis A. Influence of chlorhexidine digluconate concentration and application time on resin-dentin bond strength durability. *Eur J Oral Sci* 2009;117:587-96.
 27. Leitune VC, Portella FF, Bohn PV, Collares FM, Samuel SM. Influence of chlorhexidine application on longitudinal adhesive bond strength in deciduous teeth. *Braz Oral Res* 2011;25:388-92.
 28. Stanislawczuk R, Reis A, Loguercio AD. A 2-year *in vitro* evaluation of a chlorhexidine-containing acid on the durability of resin-dentin interfaces. *J Dent* 2011;39:40-7.
 29. Zhou J, Tan J, Chen L, Li D, Tan Y. The incorporation of chlorhexidine in a two-step self-etching adhesive preserves dentin bond *in vitro*. *J Dent* 2009;37:807-12.
 30. Pomacóndor-Hernández C, Antunes AN, Hipólito VD, Goes MF. Effect of replacing a component of a self-etch adhesive by chlorhexidine on bonding to dentin. *Braz Dent J* 2013;24:335-9.
 31. Gurgan S, Alpaslan T, Kiremitci A, Cakir FY, Yazici E, Gorucu J. Effect of different adhesive systems and laser treatment on the shear bond strength of bleached enamel. *J Dent* 2009;37:527-34.
 32. Nour El-din AK, Miller BH, Griggs JA, Wakefield C. Immediate bonding to bleached enamel. *Oper Dent* 2006;31:106-14.
 33. Salz U, Bock T. Testing adhesion of direct restoratives to dental hard tissue – A review. *J Adhes Dent* 2010;12:343-71.
 34. Kitasako Y, Burrow MF, Katahira N, Nikaido T, Tagami J. Shear bond strengths of three resin cements to dentine over 3 years *in vitro*. *J Dent* 2001;29:139-44.
 35. Shafiei F, Memarpour M. Effect of chlorhexidine application on long-term shear bond strength of resin cements to dentin. *J Prosthodont Res* 2010;54:153-8.

Author Help: Reference checking facility

The manuscript system (www.journalonweb.com) allows the authors to check and verify the accuracy and style of references. The tool checks the references with PubMed as per a predefined style. Authors are encouraged to use this facility, before submitting articles to the journal.

- The style as well as bibliographic elements should be 100% accurate, to help get the references verified from the system. Even a single spelling error or addition of issue number/month of publication will lead to an error when verifying the reference.
- Example of a correct style
Sheahan P, O'leary G, Lee G, Fitzgibbon J. Cystic cervical metastases: Incidence and diagnosis using fine needle aspiration biopsy. *Otolaryngol Head Neck Surg* 2002;127:294-8.
- Only the references from journals indexed in PubMed will be checked.
- Enter each reference in new line, without a serial number.
- Add up to a maximum of 15 references at a time.
- If the reference is correct for its bibliographic elements and punctuations, it will be shown as CORRECT and a link to the correct article in PubMed will be given.
- If any of the bibliographic elements are missing, incorrect or extra (such as issue number), it will be shown as INCORRECT and link to possible articles in PubMed will be given.